

Experimental investigations on the rheological properties of the proposed 3D printing mortar

Thi Loan Pham^{1*}, Xiao Jian Zhuang¹, Thi Hoai Thu Nguyen², Phan Anh Nguyen², Duy Thanh Trinh²

¹Department of Structural Engineering, Tongji University, 1239 Siping Road, Shanghai, PR China

²Department of Civil Engineering, Haiphong University, 171 Phan Dang Luu, Kien An District, Hai Phong City, Vietnam

Received 7 May 2021; revised 3 June 2021; accepted 23 July 2021

Abstract:

In order to explore the full potential that 3D technology can bring to the construction industry, considerable amounts of research have been carried out all over the world. However, compared to traditional construction, research related to the application of 3D printing in the construction industry is still in its infancy. Publications related to applying 3D printers in the construction field has become a hot trend in recent decades. Even after nearly three decades of global exploration into numerous projects, the complete potential of 3D printing technology in the construction industry remains unrealized. Numerous challenges impede the effective application of 3D printing in construction, with the formulation of the concrete mixture being a critical factor. This study specifically addresses mix proportion design approaches and tests, focusing on assessing the rheological properties of fresh mortar. In consideration of their practicality and relevance in construction, materials like cement, fly ash, and natural sand were chosen for the mix proportion analysis. The study employed slump-flow tests, V-funnel tests, and buildability tests to evaluate the properties of the fresh mortar. This initial exploration into mixture proportion and the methodology for assessing rheological properties in 3D printing mortar serves as a valuable reference and guide, laying the groundwork for the development of 3D printing technology in Vietnam.

Keywords: buildability test, fresh properties, mortar, slump-flow test, V-funnel test, 3D printing.

Classification number: 2.3

1. Introduction

In order to explore the full potential that 3D technology can bring to the construction industry, considerable amounts of research have been carried out all over the world. However, compared to traditional construction, research related to the application of 3D printing in the construction industry is still in its infancy. Publications related to applying 3D printers in the construction field has become a hot trend in recent decades.

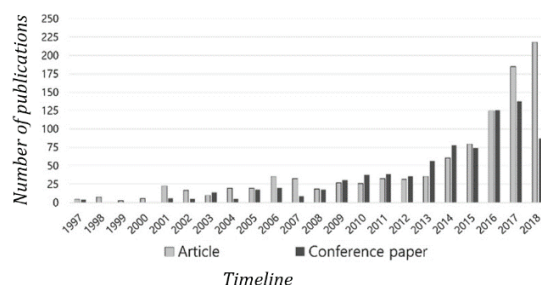


Fig. 1. Trend of publication output from 1997 to 2018 [1].

As shown in Fig. 1, since 2014 publications related to 3D printing technology has significantly increased. Many well-known buildings, bridges, as well as architectural

icons, have been constructed on-site with applying 3D printing technology [2-6]. These achievements offer insights into the full potential that 3D printing technology can bring to the construction industry.

Along with these highlighted opportunities, there have been many challenges to applying 3D printing technology on-site such as mixture proportion design, printing of large-scale components, reinforcement, etc. [7]. Among these challenges, the mixture proportion design is crucial for the preparation of 3D printing concrete. Cement-based materials are the most common ingredient and has been applied in civil structures for centuries and maintain a significant role in modern buildings as well. Moreover, successful attempts to design appropriate printing approaches for cement-based materials have been investigated by many researchers as well [8-14]. In this study, the authors employed the mixture approach by C. Zhang, et al. (2019) [15] to design the mix proportion of the mortar.

Because they are highly practical and convenient in construction, the main constituents of the mixtures mentioned here are cement, sand, and fly ash, which have been selected by many other authors [15-17]. The reason for this is to support the application of 3D printing to

*Corresponding author: Email: loanpt297@gmail.com

large-scale and on-site buildings while strictly regarding extrudability, buildability, workability, and open-time as the key requirements for 3D-printable concretes [8]. To respond to those mentioned requirements, concrete used for 3D printing technology must be as fluid as possible to be easily transported through printing system components such as pipes, nozzles, and extrusion through the printer head. Meanwhile, the concrete must be stable to prevent disunity or jamming during the flow. The fluid characteristics, setting behaviours, and viscosity performances are considered to be the most useful critical features that specify the printability and stability of concrete for 3D printing. Each behaviour can be detected and evaluated by one or more experimental methods. The slump-flow test, V-funnel test, and buildability test are simple and relatively reliable tests that are widely used [18]. Therefore, these three tests were employed in this study to evaluate the printability of the mortar.

In summary, this study suggested a mix proportion design approach and tests that access some rheological properties of the fresh mortar with highly practical applications.

2. Material preparation

In this research, ordinary Portland cement (OPC) by Chinfon and fly ash (FA) by Haiphong Thermal Power Plant were used to form the binder component. Table 1 illustrates the chemical composition of OPC and FA. According to ASTM C618, fly ash by Haiphong Thermal Power Plant is categorised as class F [19].

Table 1. Chemical composition of fly ash and ordinary Portland cement [20].

Chemical composition	Weight percentage (%)	
	Fly ash	Cement
SiO ₂	45.56	22.45
Al ₂ O ₃	23.04	5.42
Fe ₂ O ₃	5.34	3.6
TiO ₂	0.1	-
K ₂ O + Na ₂ O	7.44	1.1
CaO	1.08	61.75
MgO	1.29	1.15
P ₂ O ₅	0.2	-
SO ₃	-	2.18
MnO	0.1	-

A commercially available manufactured sand with nominal maximum aggregate size of 1.00 mm was used. The sand was quickly dried and stored in a closed plastic bag. Hence, the sand was considered as dry meaning the water content of the mixture does not contribute to the total water amount.

Superplasticizer SikaPlast®-398 SF (SP) was used to adjust the workability of the fresh mortar and its physical characteristics are given in Table 2.

Table 2. SikaPlast®-398 SF physical characteristics (SP) [21].

Physical characteristics	Test method	Test result	Specification
Specific gravity @20°C	SK-TM002	1.095	1.085-1.105
pH value @25°C	SK-TM003	5.610	4.500-6.500
Solid content @105°C	SK-TM004	30.600	29.500-31.500

Materials used for mixing mortar in this research is presented in Fig. 2.

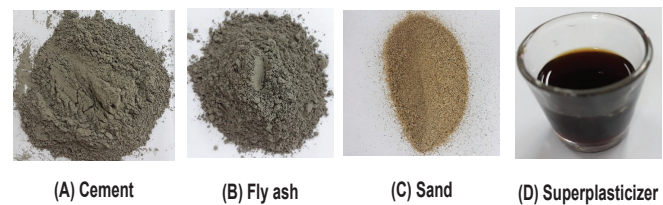


Fig. 2. Materials used for mixing mortar.

According to the successful investigations by previous authors, the authors take the water to binder ratio by weight to be 0.45. Cement and fly ash are considered as the binder. Then, the authors employed the formula of [15] to determine the amount of sand:

$$S = 4.22F + 351 \quad (1)$$

where: S is the amount of sand (gram/liter); F is the flowability of cement paste (mm); and fine sand is from natural sand by 1.00 mm square hole sieve.

The mixture proportion given in the Table 3 was prepared and then evaluated by the following tests.

Table 3. Mortar mix ratio.

Cement	Fly ash	Sand	Water	SP
0.5	0.5	2.58	0.42	0.12

Note: ratio by weight and to binder.

3. Results and discussion

3.1. Flowability test

The flowability of the binder is a critical parameter in this research. The flowability value, F, of cement paste is calculated using the sand content in Eq. 1 by C. Zhang, et al. (2019) [15].

According to the Chinese standard GB/T 8077-2012, the flowability of the binder is tested as described below [22]. Five-hundred grams of binder is prepared, and the total mixing time was five minutes. The mixing steps includes three steps as follows. Firstly, with a velocity of 140 ± 5 r/min, the binder is dry mixed for 1 min. Next, mixing is continued for 1.5 min after adding water and

superplasticizer. Finally, the binder is mixed for 2.5 min at high velocity of 285 ± 10 r/min. After the mixing, the ready-mixed binder is poured into a truncated cone. Then, the cone is vertically lifted and the flowability of the cement binder is measured immediately. The inner diameters of the top and bottom rims and the height of the cone are 36, 60, and 60 mm, respectively. The result of the flowability of the binder was 220 mm as captured in Fig. 3. The value of the flowability can range between 130 and 240 mm [15]. This value was taken to account for the amount of sand based on Eq. 1 and the result is presented in Table 3.



Fig. 3. Flowability of the tested binder.

3.2. V-funnel test

The viscosity and the deformability of fresh concrete is evaluated with the V-funnel test. The configuration of the V-shaped funnel used in this test is shown in Fig. 4. Firstly, the V-funnel is filled up with fresh mortar. Then, the funnel is lifted and the elapsed time between opening the bottom outlet and the complete emptying of the funnel without significant segregation and jamming through the narrow opening is defined as the V-funnel flow time (V_f). The mixing steps were like that of the paste for the flowability test.

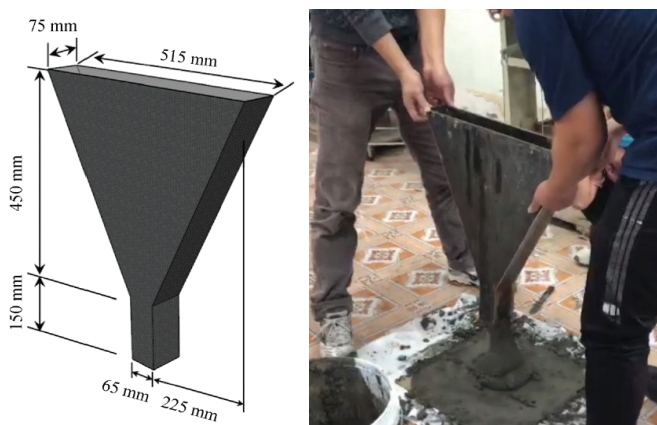


Fig. 4. Description of V-funnel test.

After filling the V-funnel with the prepared fresh mortar, it was lifted up and the mortar passed through the opening well with no segregation or jamming. The time (V_f) it took to completely empty out the mortar was 15 sec. According to previous research, this value of V_f falls within the typical ranges of 9 to 25 sec [18].

3.3. Buildability test

The remaining height of the slumped mortar cylinder under the action of gravity can be used to evaluate the yield stress and the buildability of the tested mortar. The height and diameter of the cylinder mould were 80 mm with reference to the previous experimental experience of the authors [15]. According to this reference, the buildability test procedure is as follows: initially, the cylinder mould is filled with mortar by three layers, where each layer is compacted by rodding 15 times. Then, the mould is vertically lifted, and buildability is assessed by the shape and the remaining height of the cylinder sample. If significant deformation is not observed after lifting the mould away, it can be concluded that the mortar has appropriate buildability. The mixing steps were like that of the paste for the flowability test.



Fig. 5. The slump of the sample in the buildability test.

The height of the mortar cylinder remained about 72 mm and the specimen did not deform after lifting the mould away as shown in Fig. 5. This means that the mortar has a solid ability but not enough viscosity.

Based on the slump-flow test, V-funnel test, and buildability test results, the mix proportion can be practically designed and initially evaluated by the proposed method in this study.

4. Conclusions

Based on the test results with the first analysis on mixture proportion design approach and the test used to evaluate rheological properties for the 3D printing mortar in Vietnam, some conclusions and suggestions are given:

(1) Applying 3D printing technology in construction has inevitable trends in the near future.

(2) The mixture proportion design approach presented herein is appropriate and reliable.

(3) Slump-flow test, V-funnel test, and buildability test employed in this study are highly practical for designing and initially evaluating mortar used for 3D printing technology in the construction field.

CRediT author statement

Thi Loan Pham: Data analysis and interpretation, Writing and manuscript revising; Xiao Jian Zhuang: Method, Data analysis and Writing, Thi Hoai Thu Nguyen: Method, Data analysis and Writing, Phan Anh Nguyen: Method, Data analysis and Writing, Duy Thanh Trinh: Method, Data analysis and Writing.

ACKNOWLEDGEMENTS

The authors would like to acknowledge the financial support from the National Natural Science Foundation of China (51950410599), the material support from Thanh Hung Concrete Joint Venture Company and the laboratory support at Haiphong University, Vietnam. The authors specially thank to Mr. Vu Hong Luan at VIDPOL Joint Stock Company for creating the experimental equipment.

COMPETING INTERESTS

The authors declare that there is no conflict of interest regarding the publication of this article.

REFERENCES

- [1] D. Lee, H. Kim, J. Sim, et al. (2019), "Trends in 3D printing technology for construction automation using text mining", *Int. J. Precis. Eng. Manuf.*, **20**(5), pp.871-882, DOI: 10.1007/s12541-019-00117-w.
- [2] L. Stinson (2019), "World's largest 3D-printed building completed in Dubai", <https://3dprint.com/207936/3d-printed-yhnova-house-done/archive.curbed.com/2019/12/30/21035765/world-largest-3d-printed-building-dubai-apis-cor>, accessed 5 May 2020
- [3] L. Alter (2018), "3D printed house displayed at Milan Design Week", <https://3dprint.com/207936/3d-printed-yhnova-house-done/treehugger.com/green-architecture/3d-printed-house-displayed-milan-design-week.html>, accessed 5 May 2020.
- [4] 3dsourced (2020), https://3dsourced.com/guides/3d-printed-house-2/#4_ICON, accessed 5 May 2020.
- [5] S. Saunders (2018), "Robotic 3D printed YHNOVA house officially inaugurated, tenants to move in soon", <https://3dprint.com/207936/3d-printed-yhnova-house-done/>, accessed 5 May 2020.
- [6] A. Frearson (2014), "Chinese company 3D prints 10 buildings in a day using construction waste", <https://www.dezeen.com/2014/04/24/chinese-company-3d-prints-buildings-construction-waste/>, accessed 5 May 2020.
- [7] F. Hamidi, F. Aslani (2019), "Additive manufacturing of cementitious composites: Materials, methods, potentials, and challenges", *Constr. Build. Mater.*, **218**, pp.582-609, DOI: 10.1016/j.conbuildmat.2019.05.140.
- [8] B. Zhu, J. Pan, B. Nematollahi, et al. (2019), "Development of 3D printable engineered cementitious composites with ultra-high tensile ductility for digital construction", *Mater. Des.*, **181**, DOI: 10.1016/j.matdes.2019.108088.
- [9] B. Lu, Y. Weng, M. Li, et al. (2019), "A systematical review of 3D printable cementitious materials", *Constr. Build. Mater.*, **207**, pp.477-490, DOI: 10.1016/j.conbuildmat.2019.02.144.
- [10] A. Kazemian, X. Yuan, E. Cochran, et al. (2017), "Cementitious materials for construction-scale 3D printing: Laboratory testing of fresh printing mixture", *Constr. Build. Mater.*, **145**, pp.639-647, DOI: 10.1016/j.conbuildmat.2017.04.015.
- [11] G. Ma, Z. Li, L. Wang (2018), "Printable properties of cementitious material containing copper tailings for extrusion based 3D printing", *Constr. Build. Mater.*, **162**, pp.613-627, DOI: 10.1016/j.conbuildmat.2017.12.051.
- [12] S.J. Lee, J.P. Won (2016), "Shrinkage characteristics of structural nano-synthetic fibre-reinforced cementitious composites", *Compos. Struct.*, **157**, pp.236-243, DOI: 10.1016/j.compstruct.2016.09.001.
- [13] G.W. Ma, L. Wang, Y. Ju (2018), "State-of-the-art of 3D printing technology of cementitious material - an emerging technique for construction", *Sci. China Technol. Sci.*, **61**(4), pp.475-495, DOI: 10.1007/s11431-016-9077-7.
- [14] M. Moini, J. Olek, J.P. Youngblood, et al. (2018), "Additive manufacturing and performance of architected cement-based materials", *Adv. Mater.*, **30**(43), DOI: 10.1002/adma.201802123.
- [15] C. Zhang, Z. Hou, C. Chen, et al. (2019), "Design of 3D printable concrete based on the relationship between flowability of cement paste and optimum aggregate content", *Cem. Concr. Compos.*, **104**, DOI: 10.1016/j.cemconcomp.2019.103406.
- [16] Z. Liu, M. Li, Y. Weng, et al. (2019), "Mixture design approach to optimize the rheological properties of the material used in 3D cementitious material printing", *Constr. Build. Mater.*, **198**, pp.245-255, DOI: 10.1016/j.conbuildmat.2018.11.252.
- [17] T.T. Le, S.A. Austin, S. Lim, et al. (2012), "Mix design and fresh properties for high-performance printing concrete", *Mater. Struct.*, **45**(8), pp.1221-1232, DOI: 10.1617/s11527-012-9828-z.
- [18] G. Ma, L. Wang, "A critical review of preparation design and workability measurement of concrete material for largescale 3D printing", *Front. Struct. Civ. Eng.*, **12**(3), pp.382-400, DOI: 10.1007/s11709-017-0430-x.
- [19] ASTM (2020), Standard Specification for Coal Ash and Raw or Calcined Natural Pozzolan for Use in Concrete, <https://astm.org/Standards/C618.htm>, accessed 5 May 2020.
- [20] P.T. Duc (2019), *Research on Using Fly Ash from Hai Phong Thermal Power Plant as a Mineral Additive to Improve the Properties of Bulk Concrete*, City-level science and technology research project, Haiphong Department of Science and Technology (in Vietnamese).
- [21] Sika Vietnam (2020), "SikaPlast®-398 SF", <https://vn.sika.com/vi/xay-d-ng/ph-gia-be-tong/be-tong-th-ng-phm/ph-gia-sieu-d-o/sikaplast-398-sf.html>, accessed 5 May 2020.
- [22] General Administration of Quality Supervision (2012), *GB/T 8077-2012 Methods for Testing Uniformity of Concrete Admixture*, Inspection and Quarantine of the People's Republic of China, Standardization Administration of the People's Republic of China.